

**International Congress  
Motor Vehicles & Motors 2014**

**VEHICLE AS A SAFETY FACTOR  
OF THE TRANSPORTATION ACTIVITY**

**Proceedings of Papers**



October 9<sup>th</sup> - 10<sup>th</sup>, 2014  
Kragujevac, Serbia

**International Congress  
Motor Vehicles & Motors 2014**

**VEHICLE AS A SAFETY FACTOR OF  
THE TRANSPORTATION ACTIVITY**

**Proceedings**

October 9<sup>th</sup> - 10<sup>th</sup>, 2014  
Kragujevac, Serbia

*Publisher:* Faculty of Engineering, University of Kragujevac  
Serbia, 34000 Kragujevac, Sestre Janjić 6

*For Publisher:* Prof. dr Miroslav Živković - Dean

*Editors:* Dr Božidar Krstić, prof.  
Dr Dragan Taranović, assist. prof.

*Technical preparation:* Dr Dragan Taranović, assist. prof.

*Picture on the cover.* Nemanja Lazarević

*Print CD:* Faculty of Engineering, University of Kragujevac, Kragujevac  
ISBN 978-86-6335-010-6

*Year of publication:* 2014.

*Number of copies printed:* 200

CIP - Каталогizacija u publikaciji  
Narodna biblioteka Srbije, Beograd

629.3(082)  
621.43(082)

INTERNATIONAL Congress Motor Vehicles &  
Motors (5th ; 2014 ; Kragujevac)  
Vehicle as a Safety Factor of the  
Transportation Activity : proceedings /  
International Congress Motor Vehicles &  
Motors 2014, [5], October 9th-10th, 2014,  
Kragujevac, Serbia ; [congress organizers  
Faculty of Engineering, University Kragujevac  
... [et al.] ; editors Božidar Krstić, Dragan  
Taranović]. - Kragujevac : Faculty of  
Engineering, 2014 (Kragujevac : Faculty of  
Engineering). - IX, 546 str. ; 30 cm

Tiraž 200. - Napomene i bibliografske  
reference uz tekst. - Bibliografija uz svaki rad.

ISBN 978-86-6335-010-6

Copyright © 2014 Faculty of Engineering, University of Kragujevac

*Publishing of this book is supported by:*

Ministry of Education, Science and Technological Development of the Republic of Serbia

## SCIENTIFIC BOARD

- President:** Prof. Dr Božidar Krstić, FE Kragujevac
- Secretaries:** Saša Milojević, M. Sc., FE Kragujevac
- Members:** Prof. Dr P. Andre, USA  
Prof. Dr N. Arsić, Faculty of technical Science in K.Mitrovica  
Prof. Dr B. Antić, University of Beograd, Serbia  
Prof. Dr G. Belingardi, Italy  
Prof. Dr M. Cavatorta, Italy  
Prof. Dr F. Časnji, University of Novi Sad, Serbia  
Prof. Dr B. Dalla Chiara, Italy  
Prof. Dr D. Debeljković, University of Beograd, Serbia  
Dr A. Davinić, University of Kragujevac, Serbia  
Prof. Dr M. Demić, University of Kragujevac, Serbia  
Prof. Dr A. Dimitrov, Bulgaria  
Prof. Dr Č. Duboka, University of Beograd, Serbia  
Prof. Dr R. Durković, Montenegro  
Dr J. Glišović, University of Kragujevac, Serbia  
Prof. Dr D. Gruden, Germany  
Prof. Dr A. Grujović, University of Kragujevac, Serbia  
Prof. Dr S. Žeželj, University of Beograd, Serbia  
Prof. Dr E. Hnatko, Croatia  
Dr I. Ivanović, Volvo, Sweden  
Prof. Dr A. Janković, University of Kragujevac, Serbia  
Mr S. Jovanović, Beograd, Serbia  
Prof. Dr V. Jovanović, University of Beograd, Serbia  
Prof. Dr D. Jovanović, University of Novi Sad, Serbia  
Prof. Dr K. Lipovac, University of Beograd, Serbia  
Prof. Dr B. Kegl, Slovenia  
Prof. Dr Z. Lozia, Poland  
Prof. Dr J. Lukić, University of Kragujevac, Serbia  
Mr I. Mekovec, MPPI, R. Hrvatska  
Prof. Dr S. Muždeka, University of Defence, Serbia  
Dr D. Miloradović, University of Kragujevac, Serbia  
Prof. Dr D. Ninković, Switzerland  
Prof. Dr P. Nuccio, Italy  
Prof. Dr R. Pešić, University of Kragujevac, Serbia  
Prof. Dr S. Petrović, University of Beograd, Serbia  
Prof. Dr R. Božićković, University of Dobo  
Prof. Dr S. Petković, University of Banja Luka  
Prof. Dr D. Radonjić, University of Kragujevac, Serbia  
Prof. Dr R. Radonjić, University of Kragujevac, Serbia  
Prof. Dr B. Rakićević, University of Beograd, Serbia  
Dr T. Rajić, Germany  
Prof. Dr C. Stan, Germany  
D. Tomić, Beograd, Serbia  
Dr D. Taranović, University of Kragujevac, Serbia  
Prof. Dr M. Tomić, University of Beograd, Serbia  
Prof. Dr C. Spentzas, Greece  
Prof. Dr S. Veinović, University of Kragujevac, Serbia  
Prof. Dr M. Vujanić, University of Beograd, Serbia

## ORGANIZATIONAL BOARD

**President:** Assist. prof. Dr Dragan Taranović, FE Kragujevac

**Secretaries:** Saša Milojević, M. Sc., FE Kragujevac

## CONGRESS ORGANIZERS

- Faculty of Engineering, University of Kragujevac
- Department for Motor Vehicles and Motors, FE in Kragujevac
- International Journal "Mobility & Vehicle Mechanics"
- University of Kragujevac

## CONGRESS PATRONS

- Government of the Republic of Serbia, Ministry of Education, Science and Technological Development,
- Centre for technical proper function of vehicles, FME Kragujevac
- Centre for traffic safety, FME Kragujevac
- Faculty of Engineering, University of Kragujevac
- European Union by the "*DIAUSS - Development and Improvement of Automotive and Urban Engineering Studies in Serbia*" Joint Project [JP 516729-2011] as part Tempus Program



**MVM2014-056**

**Dušan Arsić<sup>1</sup>**  
**Vukić Lazić<sup>2</sup>**  
**Srbislav Aleksandrović<sup>3</sup>**  
**Dragan Milosavljević<sup>4</sup>**  
**Božidar Krstić<sup>5</sup>**  
**Petar Marinković<sup>6</sup>**  
**Milan Đorđević<sup>7</sup>**

## **APPLICATION OF HIGH STRENGTH STEELS TO RESPONSIBLE WELDED STRUCTURES ON MOTOR VEHICLES**

**ABSTRACT:** There is constant tendency of engineers to decrease a weight of vehicles and to increase their capacity and mobility. Parallel with development of high strength steels, which starts in 90's years of last century, starts their application in industry for producing motor vehicles with special purpose (construction mechanization vehicles, fire and military vehicles, etc.). With increase of strength of used materials there are conditions for using lower thickness of cross sections what have direct influence to the weight reduction. With respect to that, one of the most used method for producing that kind of structures is welding, in this paper is analysed the weldability of used HS steel and it is proposed the optimal welding technology for welding HSS class S690QL. The assemblies and parts on one military vehicle are made of that steel. The optimal welding technology should preserve good mechanical properties in weld metal, transition zone and in HAZ as the most critical zone of the welded joint.

**KEYWORDS:** motor vehicles, high strength steel, S690QL, mechanical properties, weldability

### **INTRODUCTION**

For considered vehicle several very responsible assemblies are made, and the aim of this paper is to propose welding technology which will ensure obtaining reliable welds. In paper is estimated the weldability of high strength steel on which number of factors have influence. Some of them are chemical composition of the base metal (BM), type of filler material (FM) and welding method, amount of diffusible hydrogen from weld metal into base metal, thickness, type and positions of welds, heat input, type of applied heat treatment, sequence of welding, etc. The optimal welding parameters are based on the results obtained from the mechanical tests performed at room as well

<sup>1</sup> Dušan Arsić, Research-assistant, Faculty of Engineering, University in Kragujevac, 34000 Kragujevac, Serbia

<sup>2</sup> Vukić Lazić, Professor, Faculty of Engineering, University in Kragujevac, 34000 Kragujevac, Serbia, vlazic@kg.ac.rs

<sup>3</sup> Srbislav Aleksandrović, Professor, Faculty of Engineering, University in Kragujevac, 34000 Kragujevac, Serbia, srba@kg.ac.rs

<sup>4</sup> Dragan Milosavljević, Professor, Faculty of Engineering, University in Kragujevac, 34000 Kragujevac, Serbia, dmilos@kg.ac.rs

<sup>5</sup> Božidar Krstić, Professor, Faculty of Engineering, University in Kragujevac, 34000 Kragujevac, Serbia, bkrstic@kg.ac.rs

<sup>6</sup> Petar Marinković, Project leader, SDPR Yugoimport, 11000 Belgrade, Serbia

<sup>7</sup> Milan Đorđević, Research-assistant, Faculty of Engineering, University in Kragujevac, 34000 Kragujevac, Serbia

as at elevated temperatures, visual inspection of joint and measured hardness and metallographic examinations of some zones of welded joints, and special with regards on results obtained for impact toughness.

### **Weldability of the base metal**

The S690QL class steel belongs into a group of special thermo-mechanical (TMO) low alloyed steels. The producer provides declaration of chemical composition on delivery [1-3]. The carbon content is limited to 0.20%, so the steel should possess good weldability. Microalloying elements cause improvement of mechanical properties of those steels. Especially effective are niobium and boron, which are deoxidizing the steels and cause the fragmentation of metal grains. There are three different modifications of the S690 steels: S690Q, S690QL and S690L1, which only differ with regard to guaranteed impact toughness: S690Q – KV = 27 J at -20°C; S690QL – KV = 69 J at -40°C, S690QL1 – KV = 27 J at -60°C [2, 3]. Mass application of the high strength steel of this class occurred due to exceptional mechanical characteristics (tensile strength and yield stress) as well as favorable impact toughness. Basic data provided by the steel manufacturer can be found in corresponding references [1-3, 5].

It should be emphasized that the commercial mark of this steel is WELDOX 700 (SSAB Sweden).

It should be emphasized that application of these steels is limited for the working conditions when the temperature does not exceed 580°C, since above this limit the mechanical properties become worse [2, 3].

Weldability of high strength steels can be determined by calculating according to the equivalent carbon (CE) and proneness of the steel towards the cold cracks. Depending on formula for calculating the CE and thickness of the welded parts, the limiting values of CE vary, Table 1.

**Table 1** Values of the chemically equivalent carbon [1, 2, 4]

Mark	Thickness, mm	chemically equivalent carbon, CE, %	
		$CEV = C + \frac{Mn}{6} + \frac{Cr + Mo + V}{5} + \frac{Ni + Cu}{15}, \%$	$CET = C + \frac{Mn + Mo}{10} + \frac{Cr + Cu}{20} + \frac{Ni}{40}, \%$
S690QL	20	0.43 - 0.55	0.29 - 0.36
	30	0.46 - 0.55	0.31 - 0.36
	60	0.57 - 0.55	0.35 - 0.36

Based on results from Table 1, steel manufacturers recommend the preheating temperature that enables hydrogen diffusion from the joint zone and extending of the HAZ cooling time, for the purpose of obtaining the softer structure [1, 2, 5]. Besides the chemically equivalent carbon, one can theoretically estimate risk of appearance of cold, hot, lamellar and annealing cracks [1, 5]. According to formulas of different authors, the considered steel is highly prone to appearance of cold cracks. Risk of hot cracks is not so prominent, but risk of lamellar and annealing cracks is [1, 2]. Thus, the manner and procedure of welding should be so chosen that the reliable welded joint can be realized, which during exploitation would not be prone to appearance of any cracks that can cause brittle fracture of the welded structure.


For the S690QL steel the preheating temperature is recommended to be within range 150 – 200°C, and maximum interpass temperature should be  $T_{interpass} = 250^\circ\text{C}$  in order to prevent porosity in the weld metal caused by air turbulence, as well as worsening of the steel's mechanical properties realized by the thermo-mechanical treatment of steel

## **SELECTION OF THE OPTIMAL WELDING TECHNOLOGY**

Based on manufacturer's recommendation and experience of other users, it was decided, for responsible joints, to apply filler metals of austenitic structure of the smaller strength than the base metal for the root weld layers, while for the rest of the weld layers (filling and cover ones) to apply the filler metals of the strength similar to that of the BM.

Thus, the proposed welding technology assumes deposition of the root welds by the MMAW electrode E 18 8 Mn B 22 – diameter  $\varnothing$  3.25 mm; deposition of the filling layers is done by the GMAW electrode wire Mn3Ni1CrMo – diameter  $\varnothing$  1.2 mm (Figure 1). For deposition of the covering layers the GMAW procedure was selected due to better productivity with respect to the MMAW [1, 2]. The welded plate dimensions were 400×200×15 mm. After

deposition of the root pass 1 it was subsequently partially grooved by the graphite electrode arc-air procedure and the new root pass was deposited in the complete argon protected atmosphere by the austenite electrode 8.

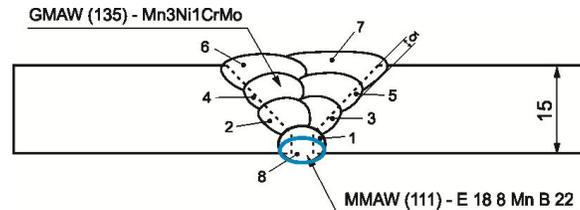

**Figure 1** Combined MMAW/GMAW deposition of weld layers

**Table 2** Chemical composition and mechanical properties of the filler metals [1, 2].

Electrode type	Chemical composition, %						Mechanical properties of weld metal			
	C	Si	Mn	Cr	Ni	Mo	R <sub>m</sub> , MPa	R <sub>p</sub> , MPa	A <sub>5</sub> , %	KV, J
E 18 8 Mn B 22 *	0.12	0.8	7	19	9	-	590 - 690	> 350	> 40	>80 (+20°C)
Mn3Ni1CrMo **	0.6	0.6	1.7	0.25	1.5	0.5	770 - 940	> 690	> 17	>47 (-40°C)


**Table 3** Welding parameters [1]

Parameters	I, A	U, V	V <sub>z</sub> , cm/s	V <sub>t</sub> , m/min	q <sub>l</sub> , J/cm	δ, mm	Shielding gas	The flow of shielding gas, l/min
Root weld (MMAW)	120	24.5	0.2	-	12000	1.7	-	-
Filler welds (GMAW)	240	25	0.35	8	14885	2	Ar/18% CO <sub>2</sub>	14

## EXPERIMENTAL INVESTIGATION OF THE WELDED JOINTS

### Tensile testing

Experimental tests of the S690QL steel specimen consisted of both mechanical tensile test and impact toughness test. The tensile test was performed on specimens prepared from the 15 mm thick plate; 4 specimens were prepared for the Base Metal (BM) tests and 4 specimens were aimed for testing the welded joint material (Figures 2 and 3) [5, 6]. Tests were performed according to standard SRPS EN 10002-1 [8].

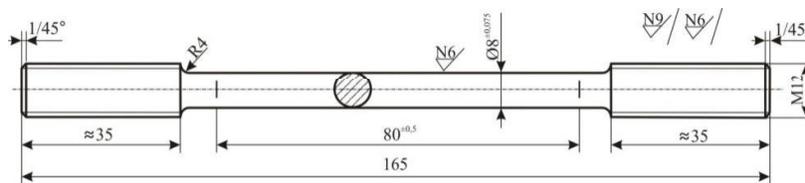

**Figure 2** Specimen for tensile testing



Specimen before testing - BM



Specimen after testing - BM



Specimen before testing - WJ



Specimen after testing - WJ


**Figure 3** Specimen appearance before and after testing

**Table 4** Experimental results of the tensile test [1-5]

Sample No	$L_0, mm$	$S_0, mm^2$	$R_{p0.2}, MPa$	$R_m, MPa$	$A_{11.3}, \%$
Base material – S690QL					
1	89.28	50.27	781.94	797.81	14.19
2	89.28	50.27	809.40	839.92	11.30
3	88.42	50.01	800.41	835.52	9.98
4	88.29	50.27	811.95	842.45	10.92
Welded joint – plate 1 (REL/MAG)					
1	89.28	50.27	809	840	11.30
2	88.42	50.27	764	831	9.77
3	86.96	49.39	760	812	5.49
4	86.96	49.39	740	804	5.38

### Impact toughness testing

Specimens were prepared for the impact toughness tests (Figure 4), according to the similar procedure as for the tensile test specimens; six aimed for testing the BM and three for testing the impact toughness of the weld metal, root metal and HAZ. Tests were done on the Charpy pendulum, both at room and lower temperatures, according to standard EN 10045-1 [9]. Table 5 gives results of the impact tests.

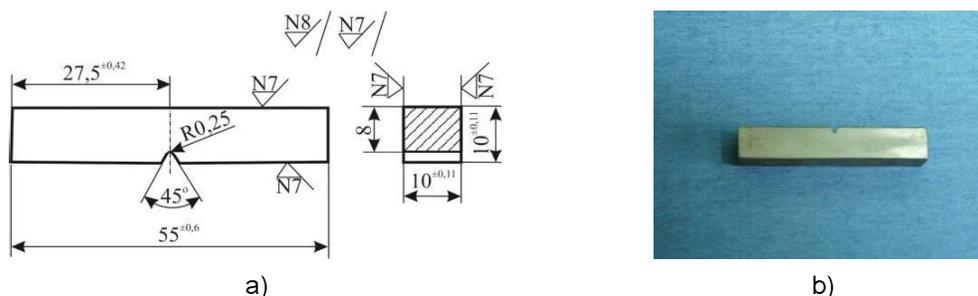

**Figure 4** Appearance of specimen for impact toughness testing: drawing (a) and photo of the specimen (b)


**Table 5** Impact energy absorbed at room and lower temperatures [2, 3]

Steel mark	Temperature, °C	Impact energy, J			
		Base material	Weld metal	Root weld metal	HAZ
S690QL	+20	235.2; 222.4; 234.7	24.2; 45.5; 34.7	85.8; 89.5; 54.1	189.2; 172.8; 209.7
	-40	219.6; 19.8; 206.1	-	-	-

\*Marked value is shown on diagram in Figure 5.

In figure 5a is shown the impact energy vs. time diagram and in figure 5b fracture surfaces appearance. Figure 5 is related to one representative specimen.

Besides the presented results, in favor of selected welding technology, were deciding also the plastic properties of the executed welded joints, estimated according to the share of the plastic fracture in the total fracture surface (Figure 2b), which was, in all the zones of the executed joint, within range 92.41 – 99.81%. That represents exceptional results from the aspect of the welded joints plasticity.

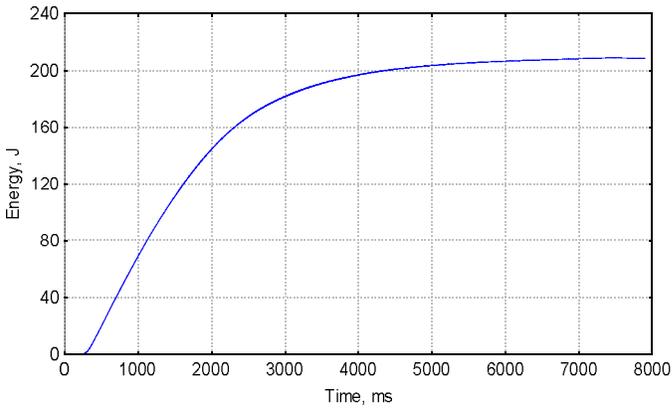

a)



b)

**Figure 5** Representative specimen – HAZ – sample 3: a) impact energy vs. time diagram; b) fracture surfaces appearance

### Hardness measurement

For hardness measurements of individual welded joints' zones, special metallographic samples were prepared, 2 per each plate (Figure 6), on which the microstructure of characteristic zones was red-off as well. Hardness was measured by the Vickers method, indentation force was 100 N, according to standard SRPS EN 1043-1:2007 [2-4].

Hardness was measured of the base metal (BM), in the HAZ and weld metal (WM) along the straight lines perpendicular to the welded joint, Figure 16. Along a single line hardness was to be measured at least at three points for each of the characteristic zones, WM, HAZ (both sides) and BM (both sides). The first indent in HAZ ought to be as close as possible to the melting zone (border WM – HAZ). This also applied for the root. Obtained results show slight deviations of values for the homogeneous zones (BM, WM), but those deviations are somewhat larger for the HAZ, as well as for the melting zone.

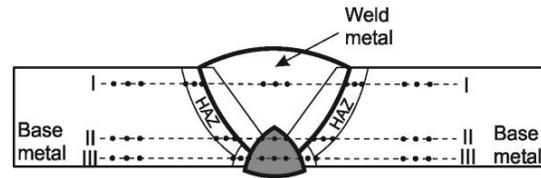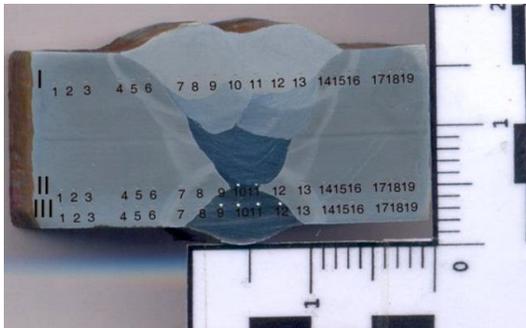


a)

b)

**Figure 6** Metallographic sample for hardness measurement and microstructure estimate (a) and hardness measurement directions (b)

In Figure 7 are shown some examples of welded construction made according to proposed welding technology and also some details from production process.

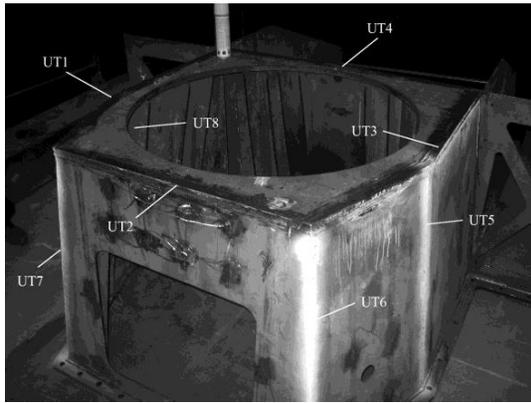

a)



b)

**Figure 7** Details from motor vehicle production process: a) ultrasonic defectoscopy and b) rear axle of a truck

## CONCLUSION

After detail analysis of the most important properties of base material and estimation of its weldability, choosing the optimal combination of filler materials, welding method and technology, and extensive model investigation, the optimal welding technology was established which has been applied on real construction. That welded construction is than installed on vehicle and was subjected to rigorous tests and it fulfilled all the requirements necessary for field work, where it turned as a very reliable one.

In establishing the optimal technology experimental results of the sample welds tensile and impact tests were used as indicators. During the tensile tests samples' fractures occurred outside the welded joint zone, what means that strength of the welded joint was higher than the base metal strength. Impact toughness was within limits required by the appropriate standards, especially in the HAZ as the most critical zone of the joint. The recorded metallographic structure revealed that appearance of the brittle martensitic structure of the welded metal was avoided.

Due to all quoted in paper, the required properties of welded joint, similar to properties of the base material, it is recommended to use this particular steel for production very responsible welded constructions.

## REFERENCES

- [1] Jovanović M., Lazić V.: *Uputstvo za zavarivanje čelika povišene jačine*, čelik: Weldom 700, Mašinski fakultet u Kragujevcu, Beograd/Kragujevac, 2008.
- [2] Arsić D.: *Ocena zavarljivosti i izbor najpovoljnije tehnologije zavarivanja čelika povišene jačine klase S690QL*, master rad, Fakultet inženjerskih nauka u Kragujevcu, Kragujevac, 2013.
- [3] D. Arsić, et. al: *Selecting the optimal welding technology of high strength steel of the S690QL class*, 19<sup>th</sup> International seminar of Ph.D. students, 29-31 January, Žilina, Slovakia, pp. 5-9.
- [4] [www.ssab.com/weldom-700-UK-data](http://www.ssab.com/weldom-700-UK-data)
- [5] V. Lazić, S. Aleksandrović, R. Nikolić, R. Prokić-Cvetković, O. Popović, D. Milosavljević, R. Čukić: *Estimates of weldability and selection of the optimal procedure and technology for welding of high strength steels*, Steel Structures and Bridges 2012, Procedia Engineering, ISSN 1877-7058, 40(2012) 310-315.
- [6] Larsson, T. B., Berglund, T.: *Handbook on WELDING of Oxelösund steels*, October 1992, Sweden.
- [7] SRPS EN 10002-1: *Metalni materijali – ispitivanje zatezanjem – Deo 1*. Institut za standardizaciju Srbije.
- [8] EN 10045-1:1990. *Charpy impact test on metallic materials*. Test method (V and U-notches). European Committee for Standardization, Brussels.