



# SERBIATRIB '25

**19<sup>th</sup> International Conference on Tribology**

14 – 16 May 2025, Kragujevac, Serbia

# PROCEEDINGS



SERBIATRIB '25



Serbian Tribology Society



University of Kragujevac  
Faculty of Engineering

# SERBIATRIB '25

19<sup>th</sup> International Conference on Tribology

14 – 16 May 2025, Kragujevac, Serbia

## PROCEEDINGS

EDITOR: Slobodan Mitrović



SERBIATRIB '25

# 19<sup>th</sup> International Conference on Tribology – SERBIATRIB '25

ISBN: 978-86-6335-128-8

- Editor:** **Slobodan Mitrović**  
Faculty of Engineering, University of Kragujevac
- Secretary:** **Dragan Džunić**  
Faculty of Engineering, University of Kragujevac
- Publisher:** **Faculty of Engineering, University of Kragujevac**  
Sestre Janjić 6, 34000 Kragujevac, Serbia
- For the Publisher:** **Slobodan Savić**  
Faculty of Engineering, University of Kragujevac
- Technical editor:** **Dragan Džunić, Živana Jovanović Pešić**  
Faculty of Engineering, University of Kragujevac
- Printed by:** **Inter Print**  
Jurija Gagarina 12, 34000 Kragujevac, Serbia
- Circulation:** 200 copies

Copyright © 2025 by Faculty of Engineering, University of Kragujevac



This book is published online with Open Access and distributed under the terms of the Creative Commons Attribution Non-Commercial License 4.0 (CC BY-NC 4.0).

The publication of this Proceedings was financially supported by the Ministry of Science, Technological Development and Innovation, Republic of Serbia.





# Contents

---

## *Fundamentals of friction and wear*

1. **THE INFLUENCE OF GRIT SIZE AND FIBER LENGTH ON THE FRICTIONAL PERFORMANCE OF COIR FIBER-REINFORCED POLYMER COMPOSITE**  
Abdullah Shalwan, Saad Alsubaie, B. F. Yousif 3
2. **METHODOLOGICAL APPROACH TO THE DEVELOPMENT PROCESS OF SINTERED FRICTION MATERIALS**  
A.Ph. Ilyushchanka, A.V. Liashok, A.N. Rogovoy 13
3. **CONTACT, FRICTION AND SEISMIC WAVES DURING SEISMOTECTONIC PROCESSES IN THE EARTH'S CRUST**  
Emilia Assenova, Evgenia Kozhoukharova 18
4. **OPTIMIZATION OF WEAR PARTICLE AND DEBRIS CLASSIFICATION**  
Jiri Stodola 27
5. **AISI10Mg POWDER CHARACTERISTICS AND WEAR MECHANISM OF PARTS FABRICATED THROUGH LASER POWDER BED FUSION TECHNIQUE**  
Ram Krishna Upadhyay 34
6. **RESEARCH PROGRESS OF METAL-ORGANIC FRAMEWORK IN TRIBOLOGY**  
Hanglin Li, Xudong Sui, Pablo Ayala, Carsten Gachot, Jiusheng Li 39
7. **PRESSURE DROP ANALYSIS IN SOLENOID-TYPE VALVES: DISCREPANCIES BETWEEN EXPERIMENTAL RESULTS AND MANUFACTURER DATA**  
Emanuel Alexander Moreno Aldana, Maurício Nogueira Frota 43
8. **THE INFLUENCE OF SOIL ABRASIVE MASS PH ON STEEL WEAR PROCESSES**  
Marcin Kowalewski, Jerzy Napiórkowski, Łukasz Konat 50
9. **OVERVIEW OF TRIBOLOGY AS AN INTERDISCIPLINARY SCIENCE**  
Gabriela Kotseva, Nikolay Stoimenov 57
10. **INFLUENCE OF SURFACE TEXTURE ON THE GENERATION INTENSITY OF AIRBORNE WEAR PARTICLES OF POLYMER MATERIALS FOR SLIDING BEARINGS**  
Wojciech Tarasiuk, Aleksander Kosarac, Tomasz Węgrzyn,  
Bożena Szczucka-Lasota, Jan Piwnik 72
11. **PHYSICS-BASED SIMPLE ANALYTICAL MODEL OF WATER FLOW THROUGH MICRO-POROUS FILTER**  
Nikola Kotorcevic, Fatima Zivic, Strahinja Milenkovic, Nenad Grujovic,  
Nikola Milivojevic 77
12. **STRUCTURAL-ENERGY CONSTANTS OF THE EVOLUTION OF THE FRICTION CONTACT**  
Sergey Vasiliy Fedorov 84

13.	<b>LIFETIME PREDICTION MODEL OF RECIPROCATING SEAL CONSIDERING VARIABLE SPEED PROFILE</b>	
	Yunhao Zhang, Chao Zhang, Shaoping Wang, Rentong Chen, Jiashan Gao	99
14.	<b>ANALYSIS OF DATASETS GENERATED DURING TRIBOLOGICAL TESTS AT NANOTRIBOMETER BY USING NONLINEAR REGRESSION ANALYSIS</b>	
	Petar Todorovic, Nikola Kotorcevic, Fatima Zivic	106
15.	<b>MATERIAL SELECTION FOR TRIBOLOGICALLY LOADED COMPONENTS</b>	
	Dragan Adamovic, Dusan Arsic, Vesna Mandic, Djordje Ivkovic, Marko Delic, Nada Ratkovic	112

### ***Tribological properties of solid materials***

16.	<b>EFFECT OF ADDITIVE ELEMENTS ON ABRASION WEAR OF AA7075 BASED ZrO<sub>2</sub>/GNP ADDED HYBRID COMPOSITES</b>	
	Şükran Katmer, Muharrem Pul, Ulvi Şeker	127
17.	<b>EFFECTS OF AGING AND SEVERE PLASTIC DEFORMATION ON TRIBOLOGICAL BEHAVIOR OF AL 7075 ALLOY</b>	
	Melih Ustalar, Muhammet Uzun, Harun Yanar, Muhammet Demirtas, Gencaga Purcek	133
18.	<b>BEHAVIOR OF THE EROSIVE WEAR OF A STEEL PIPELINE SECTION API 5L-X52 BY SOLID PARTICLES OF ALUMINUM OXIDE (AL<sub>2</sub>O<sub>3</sub>)</b>	
	Javier Alejandro Frias-Flores, Manuel Vite-Torres, Ezequiel Alberto Gallardo-Hernandez	137
19.	<b>INFLUENCE OF CONTINUOUSLY VARIABLE LATERAL FORCE ON THICKNESS OF THE MATERIAL DURING STRIP THINNING</b>	
	Slavisa Djacic, Srbislav Aleksandrovic, Dusan Arsic, Marko Delic, Djordje Ivkovic, Milan Djordjevic	146
20.	<b>DYNAMICS OF Pb EMERGENCE TO THE SURFACE IN SELF-LUBRICATING COMPOSITE MATERIALS AT ELEVATED OPERATING TEMPERATURES</b>	
	Petya Tabakova, Anna Petrova, Snezhana Atanasova, Hristo Kolev, Feyzim Hodjaoglu, Reni Andreeva, Ivan Zahariev, Georgi Avdeev, Korneli Grigorov	151
21.	<b>INFLUENCE OF B<sub>4</sub>C CONTENT AND PROCESSING CONDITIONS ON WEAR RESISTANCE OF ALUMINUM</b>	
	Sandra Gajevic, Slavica Miladinovic, Onur Güler, Serdar Özkaya, Lozica Ivanovic, Jelena Jovanovic, Blaza Stojanovic	160
22.	<b>EXPERIMENTAL STUDY ON RUBBER-GRANITE FRICTION IN DRY AND CONTAMINATED CONTACT</b>	
	Ionut Marius Nazarie, Ilie Musca, Ionut Cristian Romanu, Irina Besliu-Bancescu	168
23.	<b>THE INFLUENCE OF OXYGEN ON CORROSION AND TRIBOCORROSION OF LOW CARBON STEEL IN HYDROGEN SULFIDE ENVIRONMENT</b>	
	Myroslav Khoma, Marian Chuchman, Chrystyna Vasylyv, Vasyl Ivashkiv, Nadija Ratska, Oleh Vasylyv	176

24. **INVESTIGATION OF SHIELDED METAL ARC WELDING (SMAW)WELD INTEGRITY ON A LOW- CARBON STEEL PIPELINE USING DESTRUCTIVE MECHANICAL TESTING TECHNIQUE**  
A. E. Dele, C. V. Ossia, E. O. Diemuodeke 181
25. **INVESTIGATION OF THE TRIBOLOGICAL CHARACTERISTICS OF POLYMER MATERIALS (PLA, PLA+COPPER, AND ABS) UNDER LUBRICATED AND DRY SLIDING CONDITIONS**  
Stefan Miletic, Slobodan Mitrovic, Dragan Dzunic, Marijana Savkovic, Zivana Jovanovic Pesic, Milan Ivkovic 193
26. **APPLICABILITY OF WEAR MODELS FOR MATERIAL PARAMETER PREDICTION BASED ON PIN-ON-DISC WEAR DATA**  
Shivasharanappa V. Gubbewad, Amaresh Raichur 204
27. **TRIBOLOGICAL BEHAVIOR OF ABACA FIBER-REINFORCED EPOXY COMPOSITES: PRELIMINARY INVESTIGATIONS**  
Dragan Dzunic, Marko Milosevic, Zivana Jovanovic Pesic, Vladimir Kocovic, Suzana Petrovic Savic, Aleksandar Djordjevic, Slobodan Mitrovic 210

### ***Surface engineering and coating tribology***

28. **DEVELOPMENT OF VACUUM PLASMA STRENGTHENING HARD AND ULTRA HARD 3D AVINIT COATINGS**  
Oleksii Sagalovych, Valentin Popov, Vlad Sagalovych, Stanislav Dudnik 221
29. **STEP WAVES IN FLOWING FILMS**  
Victor Shkadov, Alexander Beloglazkin, Ignat Shishkin 234
30. **EFFECT OF W, Ni, AND Co DOPING ON THE MICROSTRUCTURE, CORROSION RESISTANCE, AND WEAR BEHAVIOR OF IRON-BASED ALLOYS PROCESSED BY SOLID-STATE SINTERING**  
Mebarki Lahcene, Hammoudi Abderrazak, Guendouz Hassan, Ivana Atanasovska 240
31. **WEAR AND SOLDERING PERFORMANCE OF BARE, NITRIDED AND PVD COATED HOT-WORKING TOOL STEEL IN CONTACT WITH Al-ALLOY CASTING**  
Pal Terek, Lazar Kovacevic, Vladimir Terek, Zoran Bobic, Branko Skoric, Marko Zagoricnik, Aljaz Drnovsek 250
32. **THE IMPORTANCE OF SUBSTRATE MATERIAL IN HIGH TEMPERATURE TRIBOLOGICAL TESTING OF PDV COATINGS – A CASE STUDY**  
Vladimir Terek, Lazar Kovacevic, Aljaz Drnovsek, Miha Cekada, Branko Skoric, Zoran Bobic, Pal Terek 259
33. **TRIBOLOGICAL PROPERTIES OF SURFACING WELDED NI60WC COATING UNDER SIMULATED PLASTICS PROCESSING CONDITIONS**  
Wangping Wu, Sheng Lin, Yang Yang 266
34. **MECHANICAL INTERLOCKING ENABLES ADHESION CONTROL UNDER UNFAVOURABLE ENVIRONMENTAL CONDITIONS**  
Marco Bruno, Luigi Portaluri, Massimo De Vittorio, Stanislav Gorb, Michele Scaraggi 279

## ***Lubricants and lubrication***

35. **VISCOMETRY ON SYNTHETIC AND FULLERENE BASED OILS AND A CFD INVESTIGATION ON COMPRESSION PISTON RING**  
Elias Tsajiridis, Alexandra Anyfanti,, Pantelis Nikolakopoulos 287
36. **NUMERICAL ANALYSIS OF THE IRONING PROCESS UNDER CONDITIONS OF VARIABLE LATERAL FORCE**  
Marko Delic, Slavisa Djacic, Srbislav Aleksandrovic, Vesna Mandic, Dusan Arsic, Djordje Ivkovic, Dragan Adamovic 297
37. **ELUCIDATION OF CHANGES IN THE MICROSTRUCTURE OF VEGETABLE LUBRICANTS BASED ON ANALYSIS OF RHEOLOGICAL PARAMETERS DETERMINED FROM THE MSD CORRELATION FUNCTION CARRIED OUT BY DWS DIFFUSION SPECTROSCOPY AND SPECTRA CARRIED OUT BY RAMAN SPECTROSCOPY**  
Rafal Kozdrach, Jolanta Drabik 303
38. **INVESTIGATION OF TRIBOLOGICAL PROPERTIES OF PROTIC IONIC LIQUIDS AS VERSATILE ADDITIVES FOR ENVIRONMENTALLY FRIENDLY WATER-BASED LUBRICANTS**  
Raimondas Kreivaitis, Artūras Kupčinskas, Milda Gumbytė, Jolanta Treinytė 314
39. **DESIGN AND SYNERGISTIC INTERACTION OF ETHERAMINE-BASED ASH-FREE ORGANIC FRICTION MODIFIERS WITH ZDDP**  
Wenjing Hu, Jiusheng Li 318
40. **CASTOR OIL BASED TERPOLYMER WITH STYRENE AND A-OLEFIN AS BIODEGRADABLE ADDITIVE IN LUBE OIL**  
Sayak P Ghosh, Pranab Ghosh 324
41. **COMPARATIVE TRIBOLOGICAL ANALYSIS OF NEW AND USED DIESEL ENGINE OILS**  
Vladimir Kocovic, Sonja Kostic, Ljiljana Brzakovic, Suzana Petrovic Savic, Zivana Jovanovic Pesic, Milos Pesic, Slobodan Mitrovic, Dragan Dzunic 330

## ***Tribology in machine elements***

42. **NUMERICAL DETERMINATION OF THE HEATING AND WEAR OF BRAKE PADS ON THE BASIS OF EXPERIMENTAL RESEARCHES**  
Nadica Stojanovic, Ali Belhocine, Oday I. Abdullah, Zeljko Djuric, Ivan Grujic 339
43. **THE NUMERICAL INVESTIGATION OF THE WEAR AND HEATING OF ENGINE PISTON AND CYLINDER FOR THE CASE OF TRIBOLOGICAL INSERTS APPLICATION**  
Ivan Grujic, Zeljko Djuric, Nadica Stojanovic 347
44. **MODIFICATION OF GATE VALVE SEALING ELEMENT TO ENHANCE THE WEAR RESISTANCE**  
Jamaladdin Aslanov, Khalig Mammadov 352

45.	<b>ANALYSIS OF PRESSURE DISTRIBUTION IN 3D-PRINTED SLIDING BEARINGS USING HERTZIAN CONTACT THEORY</b>	Ivan Simonovic, Aleksandar Marinkovic	360
46.	<b>INFLUENCE OF OPERATING CONDITIONS ON THE POWER LOSSES OF THE WORM GEARBOX</b>	Aleksandar Skulic, Sandra Gajevic, Sasa Milojevic, Milan Bukvic, Igor Lavrnic, Blaza Stojanovic	366
47.	<b>CASE STUDY ON SUITABILITY OF RAIL GREASE PERFORMANCE FOR LIGHT RAIL TRANSIT (LRT) KELANA JAYA, MALAYSIA</b>	Nadia Nurul Nabihah Ahmad Fuad, Izzatul Hamimi Abdul Razak, Mohamad Ali Ahmad, Wan Ahmad Syahmi Wan Amir Zaki, Mohamad Nasrulhisyam Sobri, Sabrina Karim	373
48.	<b>EFFECT OF CAVITATION EROSION ON MATERIAL MECHANICAL PROPERTIES AND MACHINE ELEMENTS PERFORMANCE</b>	Pavle Ljubojevic, Tatjana Lazovic, Marina Dojcinovic, Jovana Antic	383
49.	<b>THE ROLE OF TRIBOLOGY IN IMPROVING THE PERFORMANCE OF MACHINERY SYSTEMS</b>	Milica Utvic, Bojan Stojcetovic, Milan Misic, Anja Jovanovic	391
50.	<b>TRIBOLOGICAL ASPECTS OF IDENTIFICATION OF THE KEY CAUSES OF REDUCTION IN THE EFFICIENCY OF AXIAL PISTON WATER HYDRAULIC PUMPS</b>	Nenad Todic, Slobodan Savic, Zivojin Stamenkovic, Blaza Stojanovic	396

### ***Tribology in manufacturing processes***

51.	<b>PERFORMANCE CHARACTERISTICS OF ECO-FRIENDLY AGROBIO-WASTES AS MOLD ADDITIVES ON MECHANICAL PROPERTIES OF AISiMg ALLOY</b>	Maruf Yinka Kolawole, Sefiu Adekunle Bello, Ayodeji Sulaiman Olawore, Tunji Adetayo Owoseni	407
52.	<b>THE INFLUENCE OF THE HARD-FACED LAYERS PATTERN ON THE WEAR RESISTANCE OF THE WHEEL LOADER'S BUCKET TEETH</b>	Djordje Ivkovic, Dusan Arsic, Vukic Lazic, Marko Delic, Andjela Ivkovic, Petra Bujnakova	419
53.	<b>ANALYSIS OF THE INFLUENCE OF HOT FORGING PROCESS PARAMETERS ON TOOL WEAR USING THE FINITE ELEMENT METHOD</b>	Marko Delic, Milos Delic	424
54.	<b>FUNCTIONAL ANALYSIS OF SURFACE ROUGHNESS</b>	Suzana Petrovic Savic, Milos Zivanovic, Marko Pantic, Dragan Dzunic, Vladimir Kocovic, Zivana Jovanovic Pesic, Aleksandar Djordjevic	432
55.	<b>THE INFLUENCE OF CUTTING DEPTH ON SURFACE ROUGHNESS OF 3D PRINTED PARTS</b>	Strahinja Djurovic, Milan Ivkovic, Nikolaj Velikinac, Dragan Lazarevic, Milan Misic, Bojan Stojcetovic, Stefan Miletic	439

56. **INFLUENCE OF CUTTING CONDITIONS ON SURFACE ROUGHNESS OF PA AND PA15**  
Milan Ivkovic, Stefan Mihailovic, Strahinja Djurovic, Stefan Miletic,  
Bogdan Zivkovic, Bogdan Nedic, Suzana Petrovic Savic 443
57. **ANALYSIS OF THE EFFECTS OF CUTTING SPEED AND FOCUS POSITION ON  
OXIDATION MARKS IN FIBER REACTIVE LASER CUTTING**  
Milos Madic, Dusan Petkovic, Miroslav Mijajlovic, Milan Banic, Milan Trifunovic 450
58. **FINITE ELEMENT INVESTIGATION OF THE EFFECT OF FRICTION CONDITIONS AND  
CUTTING ENVIRONMENT IN TURNING OF AISI H13 HARDENED STEEL**  
Nikolaos E. Karkalos, Nikolaos A. Fountas, Nikolaos M. Vaxevanidis 456

### ***Design and calculation of tribocontacts***

59. **DESIGN AND TESTING OF PIN ON DISC TRIBOMETER: FINK-POD2025**  
Andjela Perovic, Mirjana Piskulic, Stefan Cukic, Milos Matejic, Blaza Stojanovic 465
60. **FINITE ELEMENT ANALYSIS OF STRESS AND CONTACT PRESSURE IN STEEL PLATES  
UNDER VARYING FRICTION COEFFICIENTS**  
Vladimir Milovanovic, Milos Pesic, Snezana Vulovic, Zivana Jovanovic Pesic,  
Miroslav Zivkovic 472
61. **DESIGN AND TESTING OF A MODULAR TRIBOMETER FOR ANTI-FRICTION COATING  
ANALYSIS IN OCTG APPLICATIONS**  
Igor' Yu. Pyshmintsev, Andrey Golyshev, Alexey Lovyagin 480
62. **A REVIEW OF LINEAR RECIPROCATING TRIBOMETERS: DESIGN AND APPLICATIONS**  
Jovana Markovic, Marija Matejic, Milos Matejic, Jasmina Skerlic, Bojan Bogdanovic 486

### ***Biotribology***

63. **WEAR IN RESTORATIVE DENTISTRY/TEETH AND DENTAL MATERIALS**  
Kivanc Dulger, Gencaga Purcek 495
64. **EFFECT OF ACETABULAR CUP THICKNESS ON THE MAXIMUM CONTACT PRESSURE  
IN NITRIDED GRADE2 TDN – UHMWPE HIP ENDOPROSTHESES**  
Myron Czerniec, Jerzy Czerniec 514
65. **EFFECT OF ELECTRON BEAM PROCESSING PARAMETERS ON THE SURFACE  
ROUGHNESS OF TITANIUM SAMPLES**  
Zivana Jovanovic Pesic, Aleksandra Vulovic, Strahinja Milenkovic,  
Djordje Ilic, Dragan Dzunic 522

### ***Other topics related to tribology***

66. **FLEXURAL, COMPRESSIVE AND FRACTURE TOUGHNESS OF DELONIX REGIA POD-  
EGGSHELL PARTICLE REINFORCED VIRGIN LOW-DENSITY POLYETHYLENE  
NANOCOMPOSITES**  
Sefiu Adekunle Bello, Maruf Yinka Kolawole, Adijat Ashifat, Davina Ajetomobi,  
Jeremiah Ponle, Suleiman Danjuma Daudu, Mohammed Kayode Adebayo,  
Aisha Mayowa Akintola 529

67.	<b>MODELLING AND STATISTICAL ANALYSIS OF FLANK WEAR DURING TURNING OF Co-Cr-Mo ALLOY</b>	
	Aleksandar Milosevic, Sanda Simunovic, Mario Sokac, Zeljko Santosi, Vladimir Kocovic, Djordje Vukelic	541
68.	<b>HYBRID METAHEURISTIC ALGORITHM: A NOVEL APPROACH FOR INDUSTRIAL OPTIMIZATION CHALLENGES</b>	
	Hammoudi Abderazek, Aissa Laouissi, Mourad Nouioua, Ivana Atanasovska	550
69.	<b>TRIBOCORROSION OF ALUMINUM ALLOY IN A CHLORIDECONTAINING ENVIRONMENT INHIBITED BY A MALTODEXTRIN-BASED COMPOSITION</b>	
	Sergiy Korniy, Marjana Tymus, Ivan Zin, Nadiia Rats'ka, Bogdan Datsko	557
70.	<b>IMPACT TESTS FOR TWO COMPOSITES FOR MARINE APPLICATIONS</b>	
	Ioana Gabriela Chiracu, Constantin Georgescu, George Cătălin Cristea, George Ghiocel Ojoc, Mihail Boțan, Alexandru Viorel Vasiliu, Lorena Deleanu	564
71.	<b>ANALYSIS OF ROLLING RESISTANCE PARAMETERS IN GRAVITY FLOW RACKS FOR HEAVY-DUTY APPLICATIONS</b>	
	Mirjana Piskulic, Rodoljub Vujanac, Nenad Miloradovic	579
72.	<b>IMPACT OF GRAPHENE ON THE PROPERTIES OF PHASE CHANGE MATERIAL</b>	
	Kapilan Natesan, Sriram Mukunda, Vidhya P, Shivarishika K	585
73.	<b>STUDY ON MECHANICAL AND MICROSTRUCTURAL PROPERTIES OF 7075Al/SiC METAL MATRIX COMPOSITES</b>	
	Sriram Mukunda, Kapilan Natesan	592
74.	<b>POSSIBILITIES OF APPLYING ARTIFICIAL INTELLIGENCE IN THE FIELD OF TRIBOLOGICAL RESEARCH</b>	
	Milan Eric, Miladin Stefanovic, Slobodan Mitrovic, Dragan Dzunic, Vladimir Kocovic, Zivana Jovanovic Pesic, Suzana Petrovic Savic, Aleksandar Djordjevic, Marko Pantic	598
75.	<b>INFLUENCE OF PRESS-FIT DIMENSIONS ON REPEATED ASSEMBLY OF BALL BEARINGS INTO 3D PRINTED HOUSINGS</b>	
	Strahinja Milenkovic, Zivana Jovanovic Pesic, Nenad Petrovic, Dalibor Nikolic, Nenad Kostic	609



Serbian Tribology  
Society

# SERBIATRIB '25

19<sup>th</sup> International Conference on  
Tribology



Faculty of Engineering  
University of Kragujevac

Kragujevac, Serbia, 14 – 16 May 2025

Research paper

DOI:10.24874/ST.25.207

## COMPARATIVE TRIBOLOGICAL ANALYSIS OF NEW AND USED DIESEL ENGINE OILS

Vladimir KOCOVIĆ<sup>1</sup>, Sonja KOSTIĆ<sup>2</sup>, Ljiljana BRZAKOVIĆ<sup>3</sup>, Suzana PETROVIĆ SAVIĆ<sup>1</sup>, Zivana JOVANOVIĆ PESIĆ<sup>1</sup>, Milos PESIĆ<sup>4</sup>, Slobodan MITROVIĆ<sup>1</sup>, Dragan DZUNIC<sup>1,\*</sup>

<sup>1</sup>University of Kragujevac, Faculty of Engineering, Kragujevac, Republic of Serbia

<sup>2</sup>Academy of Professional Studies Šumadija, Department in Kragujevac, Kragujevac, Serbia

<sup>3</sup>Academy of Professional Studies Šumadija, Department in Trstenik, Trstenik, Serbia

<sup>4</sup>University of Kragujevac, Institute for Information Technologies - National Institute of the Republic of Serbia, Kragujevac, Republic of Serbia

\*Corresponding author: dzuna@kg.ac.rs

**Abstract:** *This study investigates the tribological behaviour of aluminium samples lubricated with new and used SAE 10W-40 and SAE 30 engine oils under controlled laboratory conditions. Tribological testing was performed using a block-on-disc configuration on a TPD-95 tribometer, following ASTM G77 standards. All tests were conducted at a sliding speed of 0.5 m/s, an applied load of 20 daN, and a test duration of 600 seconds, with continuous lubrication provided. Results show that, for both oil types, the used oils exhibited a lower coefficient of friction compared to the new oils throughout the entire sliding distance. In the case of SAE 10W-40, used oil led to both reduced friction and significantly lower material loss, while in the SAE 30 group, despite lower friction, the used oil resulted in a slightly larger wear scar and increased worn volume compared to the new oil. These findings suggest that oil degradation products can temporarily enhance lubrication performance but may compromise long-term wear protection.*

**Keywords:** *aluminium alloys, engine oils, tribological behaviour, wear analysis, oil degradation*

### 1. INTRODUCTION

Aluminium is increasingly being used in the construction of internal combustion engines, particularly in the production of sliding bearings, pistons, and connecting rods, due to its low specific weight, corrosion resistance, good thermal conductivity, recyclability, and contribution to improved fuel efficiency. However, its mechanical properties—especially its limited wear resistance—require special attention with regard to surface protection, where the quality of engine oil plays a crucial role [1].

The quality of engine oil has a significant and multifaceted impact on the wear of aluminium surfaces. Wear is one of the primary mechanisms of material degradation in engine blocks, and several factors contribute to this process: the presence of hard particles and chemicals in cooling and lubricating fluids causes abrasive and corrosive wear; the impact of hot air and gases leads to erosive wear; friction between the cylinder wall and piston rings can induce adhesion even in the presence of oil; and material fatigue also plays a considerable role. High-quality engine oils reduce friction, ensure optimal viscosity, and

contain additives that protect aluminium components from wear and corrosion [2, 3].

Engine oil plays a multifaceted role in maintaining engine functionality. It forms a thin lubricating film between metal components, reducing direct contact and friction, which directly decreases wear and extends engine lifespan. SAE30 oil is a traditional, single-grade lubricant designed for stable and warm operating conditions, whereas 10W-40 is a multigrade product that offers a significantly broader temperature range and improved engine protection under various conditions, including cold starts and heavy engine loads [4].

During operation, engine oil naturally undergoes degradation as it is exposed to high temperatures, pressures, and the chemical effects of fuel combustion. Throughout this process, the oil changes colour, loses clarity, darkens, and develops an unpleasant odour—these being the initial indicators of oil aging and contamination. Changes in kinematic viscosity are particularly critical. Reduced viscosity leads to a drop in oil pressure and results in increased friction, thereby accelerating the wear of piston rings, bearings, and other vital engine components. On the other hand, excessively high viscosity impairs oil circulation and hinders the proper formation of the lubricating film at frictional contact points [5–7].

The recycling of engine oils plays a key role in the sustainable use of resources, environmental protection, and the mitigation of ecological problems caused by toxic substances present in used oils. The main challenge in recycling SAE30 and SAE10W-40 engine oils lies in their complex chemical structure and the contamination that occurs during use. These oils contain additives and chemicals that undergo reactions during engine operation, producing harmful by-products that require specialized processes for their removal [8]. In their study, Hisham et al. investigated a mixture of waste cooking oil and SAE 10W-40, aiming to reduce wear and friction on the aluminium piston skirt. They concluded that increasing the concentration of waste cooking oil reduces the

viscosity of the bio-lubricant, which leads to increased friction, likely due to corrosive wear [9].

Given the complexity of oil degradation processes and their impact on tribological performance, the present study focuses on a comparative analysis of the wear behaviour of aluminium samples lubricated with new and used SAE 10W-40 and SAE 30 engine oils under standardized laboratory conditions.

## 2. MATERIALS AND METHOD

This study examined two types of commercial motor oils for their tribological potential during the experiment. The tested oils were SAE 10W-40 and SAE 30. Table 1 presents the main characteristics of all motor oils used for experimental testing in this study.

**Table 1.** Physicochemical Properties of SAE 10W-40 and SAE 30 Motor Oils

Property	SAE 10W-40	SAE 30
Viscosity Index	155	95
Density (g/ml @ 15.6°C, ASTM D4052)	0.86	0.88
Flash Point (°C, ASTM D93)	212	210
Pour Point (°C, ASTM D97)	-45	-30

Experimental testing was conducted using the TPD-95 tribometer, which is equipped with computer-controlled precision to maintain consistent and repeatable test conditions. The testing procedure followed the ASTM G77 standard, which outlines methods for assessing the wear characteristics of materials. The tribometer operates based on a block-on-disc configuration, where a stationary block is pressed against a rotating disc under a defined load. This setup effectively replicates practical friction and wear scenarios. It enables precise evaluation of tribological parameters such as wear rate and coefficient of friction, thereby providing dependable data for analysing material behaviour under sliding contact. The disc is made of EN 25CrMo4 steel, featuring a hardness of 60–64 HRC and ground surface finish, while all test blocks are made of EN AW-

6060 aluminium alloy. The disc has a diameter of 35 mm, and the block dimensions are 15 × 10 × 6.35 mm, in accordance with ASTM G77 standards.

Prior to testing, all aluminium blocks were subjected to a standardized surface preparation process to ensure uniform initial conditions. Each block was ground sequentially on all sides using a mechanical grinder. The grinding procedure was performed at a rotational speed of 500 revolutions per minute, with each side being ground for a duration of 1 minute. To achieve a progressively finer surface finish and minimize surface roughness, the following grades of silicon carbide abrasive papers were used in succession: P600, P1200, and P2000. This preparation ensured consistent surface conditions across all samples, which is critical for the reliability and repeatability of tribological testing.

All tribological tests were conducted under identical operating conditions to ensure the comparability and repeatability of results. The applied normal load was set to 20 daN, while the sliding speed was maintained at 0.5 m/s. Each test was performed over a total sliding duration of 600 seconds, corresponding to a well-defined sliding distance. Continuous lubrication was provided throughout the testing process via a reservoir system with a total capacity of 30 ml, ensuring a stable supply of lubricant to the contact interface. Accordingly, four distinct test groups were defined and labeled as follows:

1. **Al-10W-40-N** sample test: This group represents aluminium samples tested using new SAE 10W-40 multigrade engine oil. The oil was unused prior to the experiment, providing a baseline for evaluating the tribological performance of fresh lubricant under defined test conditions.
2. **Al-10W-40-U** sample test: In this group, aluminium samples were tested using used SAE 10W-40 oil, collected after extended service. The aim was to assess the effect of

oil degradation and contamination on friction and wear characteristics.

3. **Al-SAE30-N** sample test: This group involved testing aluminium samples with new SAE 30 monograde oil. As with the first group, the oil was in its original, uncontaminated state, allowing for a controlled evaluation of tribological properties.
4. **Al-SAE30-U** sample test: This group consisted of tests performed using used SAE 30 oil, previously employed in engine operation. The test was intended to simulate real-world conditions in which the lubricant has undergone thermal and mechanical degradation.

The volume of the worn material was calculated using the following expression:

$$V = \left( \frac{306.25}{2} \cdot 2 \arcsin\left(\frac{b}{35}\right) - \frac{\sqrt{306.25 - \frac{b^2}{4}} \cdot b}{2} \right) \cdot 6.35 \quad (1)$$

where:

$b$  – width of the wear mark

306.25 – square of the disc's radius

6.35 – width of the block in mm.


This formula accounts for the geometric characteristics of the block-on-disc contact and is based on the analytical calculation of the worn area profile. Specifically, it first determines the cross-sectional area of the wear scar generated by the curved contact surface between the block and the disc, treating the disc as part of a circular arc. Multiplying this cross-sectional area by the known width of the block (6.35 mm) yields the volume of material lost due to wear.

The arcsine function captures the curvature effect of the disc in the contact zone, while the second term corrects for the material removed outside the direct contact area, ensuring a precise estimation of volumetric wear. This

approach provides a more accurate evaluation compared to simple approximations, particularly when the wear scar spans a significant portion of the disc's surface.

### 3. RESULTS AND DISCUSSION

Figure 1 presents the coefficient of friction ( $\mu$ ) as a function of sliding distance ( $s$ ) for aluminium samples lubricated with new and used SAE 10W-40 engine oil. Each curve represents the average trend from three individual measurements conducted under identical tribological conditions.

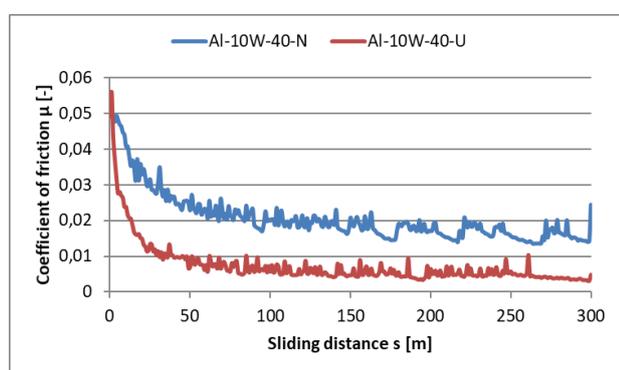


**Figure 1.** Coefficient of friction as a function of sliding distance for Al-10W-40-N and Al-10W-40-U samples

The Al-10W-40-N sample (blue curve) demonstrates an initially high coefficient of friction, which rapidly decreases during the running-in phase and stabilizes around a value of approximately 0.02–0.025. In contrast, the Al-10W-40-U sample (red curve), lubricated with used oil, exhibits significantly lower friction values throughout the entire test, stabilizing below 0.01 after the initial sliding distance. Both curves show small oscillations, but the used oil consistently yields lower friction levels compared to the new oil.

Notably, the used oil (Al-10W-40-U) exhibited a consistently lower coefficient of friction compared to the new oil (Al-10W-40-N) across the entire sliding distance. This trend may initially seem counterintuitive, as new oil is generally expected to provide superior lubrication due to the full presence of additive packages and stable viscosity. It is important to note that the present investigation represents

preliminary research conducted under controlled laboratory conditions, at temperatures lower than typical engine operating temperatures. As such, the tribological behaviour observed for the used oil at these conditions may not necessarily reflect its performance at elevated, real-world temperatures. Further testing under operational thermal loads is required to validate whether the same frictional trends persist in actual service conditions.

Figure 2 shows the variation of the coefficient of friction as a function of sliding distance for aluminium samples lubricated with new and used SAE 30 monograde oil (Al-SAE30-N and Al-SAE30-U, respectively).

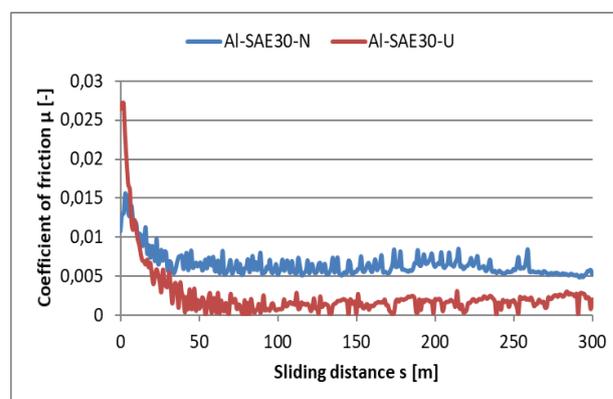

**Figure 2.** Coefficient of friction as a function of sliding distance for Al-SAE30-N and Al-SAE30-U samples

Similar to the trends observed with SAE 10W-40, the used oil again resulted in a lower friction coefficient throughout the test duration. The Al-SAE30-N sample displayed an initial peak followed by a steady-state friction coefficient around 0.006–0.007, while the Al-SAE30-U sample stabilized below 0.004. Each curve represents the average behaviour recorded across three repeated measurements.

The results obtained for SAE 30 oils further reinforce the trend observed with multigrade SAE 10W-40 oil, where the used lubricant consistently produced a lower coefficient of friction. In the case of SAE 30, which inherently lacks the viscosity modifiers present in multigrade oils, the difference in friction between new and used conditions appears

even more pronounced in the steady-state region.

It should be emphasized that this study is part of an initial investigation carried out at ambient temperatures. While the results suggest that used oil may offer lower friction in controlled environments, such behaviour may not be maintained under real engine operating conditions. Additional testing at elevated temperatures and in the presence of thermal cycling is necessary to assess the full tribological implications of oil degradation.

The average width of the wear scar (in mm) was measured for each test group and is presented below:

1. Al-10W-40-N sample test: 2.643 mm
2. Al-10W-40-U sample test: 2.000 mm
3. Al-SAE 30-N sample test: 1.429 mm
4. Al-SAE 30-U sample test: 1.616 mm


The measured wear scar widths provide additional insight into the wear mechanisms involved in the tribological contact. For both oil types, the used oils not only exhibited lower friction coefficients but also resulted in narrower wear scars, with the exception of SAE 30, where the used oil produced a slightly wider scar than the new oil.

The Al-10W-40-U sample demonstrated a reduction in wear scar width of approximately 24% compared to the new oil, indicating that the aged oil maintained sufficient lubricating capacity to reduce material removal. This is consistent with the observed lower coefficient of friction and may be attributed to the formation of boundary films composed of oxidation and degradation products that offer partial surface protection.

On the other hand, the Al-SAE 30-U sample showed a slightly increased wear scar width relative to the new SAE 30 oil, despite its lower friction. This discrepancy suggests that while used SAE 30 oil may reduce friction due to altered viscosity or surface-active degradation by-products, its diminished additive content

may fail to prevent wear progression effectively. This highlights the complex and sometimes non-linear relationship between friction and wear, where reduced friction does not always guarantee improved wear resistance.

Figure 3 presents the comparison of worn material volumes for all tested aluminium samples lubricated with new and used SAE 10W-40 and SAE 30 engine oils. The Al-10W-40-N sample exhibited the highest worn volume, reaching approximately  $0.559 \text{ mm}^3$ , whereas the Al-10W-40-U sample showed a significant reduction, with a worn volume of  $0.242 \text{ mm}^3$ . In the case of SAE 30 oils, the new oil (Al-SAE30-N) resulted in the lowest recorded worn volume of  $0.088 \text{ mm}^3$ , while the used oil (Al-SAE30-U) showed a slightly higher worn volume of  $0.128 \text{ mm}^3$ .

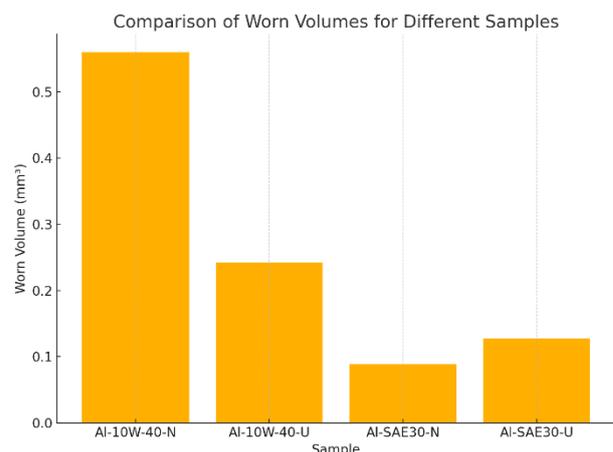

**Figure 3.** Comparison of worn volumes for Al-10W-40-N, Al-10W-40-U, Al-SAE30-N, and Al-SAE30-U samples

The analysis of worn volumes provides important insights that complement the friction measurements. For the SAE 10W-40 oil group, the used oil not only produced a lower coefficient of friction but also substantially reduced material loss, indicating that under the given test conditions, degraded oil maintained a protective boundary layer that effectively minimized wear.

In contrast, for the SAE 30 oil group, although the used oil exhibited a slightly lower friction coefficient, the worn volume increased compared to the new oil. This suggests that in

the case of SAE 30, degradation processes during service may have led to insufficient replenishment of protective additives, resulting in less effective wear resistance despite the reduced friction.

These findings confirm that friction reduction alone cannot be considered a sufficient indicator of lubricant performance. The complex interplay between viscosity, chemical composition, and surface interactions must be taken into account to fully understand the behaviour of new and used oils under tribological loading.

#### 4. CONCLUSION

The tribological performance of new and used SAE 10W-40 and SAE 30 engine oils was evaluated under identical test conditions using a block-on-disc tribometer. In both oil categories, the used oils demonstrated a consistently lower coefficient of friction compared to their new counterparts. This trend was evident across the entire sliding distance and observed in all three repeated measurements per group.

The reduced friction in used oils may be attributed to the presence of degradation products and polar compounds formed during service, which can act as surface-active agents and temporarily enhance lubricity. However, this apparent advantage must be interpreted with caution, as it does not necessarily correlate with superior overall performance or wear protection. The depletion of critical additives in used oils can increase the risk of corrosive or abrasive wear mechanisms, particularly under elevated temperatures and dynamic operating conditions.

The complex relationship between friction and wear: a lower coefficient of friction does not inherently guarantee superior anti-wear performance. The chemical stability, additive retention, and viscosity behaviour of the lubricant are critical factors that must be

evaluated alongside friction measurements to obtain a complete understanding of its tribological effectiveness.

#### ACKNOWLEDGEMENT

This paper is the result of research conducted under the author's contract No. 451-03-137/2025-03/200107, dated February 4, 2025, and partly supported by the Ministry of Science, Technological Development and Innovation, Republic of Serbia, Agreement No. 451-03-136/2025-03/200378.

#### ORCID iDs

Vladimir KOCOVIĆ [0000-0003-1231-0041](https://orcid.org/0000-0003-1231-0041)

Sonja KOSTIĆ [0000-0002-6120-6139](https://orcid.org/0000-0002-6120-6139)

Ljiljana BRZAKOVIĆ [0000-0003-0583-0583](https://orcid.org/0000-0003-0583-0583)

Suzana PETROVIĆ SAVIĆ [0000-0002-5629-6221](https://orcid.org/0000-0002-5629-6221)

Zivana JOVANOVIĆ PESIĆ [0000-0002-1373-0040](https://orcid.org/0000-0002-1373-0040)

Milos PESIĆ [0000-0002-3405-5216](https://orcid.org/0000-0002-3405-5216)

Slobodan MITROVIĆ [0000-0003-3290-7873](https://orcid.org/0000-0003-3290-7873)

Dragan DZUNIC [0000-0002-1914-1298](https://orcid.org/0000-0002-1914-1298)

#### REFERENCES

- [1] Z. Aleš, J. Pavlů, J. Svobodová, M. Kučera, M. Hromasová, and M. Pexa, "Impact of contaminants in motor oil on the wear of aluminum parts of the internal combustion engine," *Manufacturing Technology*, vol. 17, no. 5, pp. 647–652, 2017, doi: 10.21062/ujep/x.2017/a/1213-2489/MT/17/5/647.
- [2] M. S. Kaiser and S. Dutta, "Wear behavior of commercial aluminium engine block and piston under dry sliding condition," *International Journal of Materials and Metallurgical Engineering*, vol. 8, no. 8, pp. 860–865, 2014.
- [3] S. Rațiu, A. Josan, V. Alexa, V. G. Cioată, and I. Kiss, "Impact of contaminants on engine oil: A review," *Journal of Physics: Conference Series*, vol. 1781, p. 012051, 2021, doi: 10.1088/1742-6596/1781/1/012051.
- [4] B. Zhmud, A. Coen, and K. Zitouni, "Fuel economy engine oils: Scientific rationale and controversies," *SAE Technical Paper*, no. 2021-24-0067, 2021, doi: 10.4271/2021-24-0067.
- [5] K. Sakamoto, F. Mizutani, M. Shimomura, K. Yama, T. Matsunaga, and S.-S. Lee, "Evaluation

- of engine oil degradation based on viscosity and transmitted light intensity measurements,” *Sensors and Actuators A: Physical*, vol. 361, p. 114597, 2023, doi: 10.1016/j.sna.2023.114597.
- [6] R. Smigins, K. Amatnieks, A. Birkavs, K. Górski, and S. Kryštopta, “Studies on engine oil degradation characteristics in a field test with passenger cars,” *Energies*, vol. 16, p. 7955, 2023, doi: 10.3390/en16247955.
- [7] Y. N. Bezborodov, N. N. Lysyannikova, and E. G. Kravcova, “Results of the study of anti-wear properties of the exhaust motor oil,” *Procedia Engineering*, vol. 150, pp. 654–660, 2016, doi: 10.1016/j.proeng.2016.07.062.
- [8] K. K. Syrmanova, A. Y. Kovaleva, Z. B. Kaldybekova, N. Y. Botabayev, T. N. Botashev, and B. Y. Beloborodov, “Chemistry and recycling technology of used motor oil,” *Oriental Journal of Chemistry*, vol. 33, no. 6, pp. 3195–3199, 2017, doi: 10.13005/ojc/330665.
- [9] S. Hisham, K. Kadirgama, D. Ramasamy, M. M. Noor, A. K. Amirruddin, G. Najafi, and M. M. Rahman, “Waste cooking oil blended with the engine oil for reduction of friction and wear on piston skirt,” *Fuel*, vol. 205, pp. 247–261, 2017, doi: 10.1016/j.fuel.2017.05.068.